

इंटरनेट

मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan


“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 228-2 (1987): Methods for Chemical Analysis of Steels, Part 2: Determination of Manganese in Plain-Carbon and Low Alloy Steels by Arsenite Method [MTD 4: Wrought Steel Products]

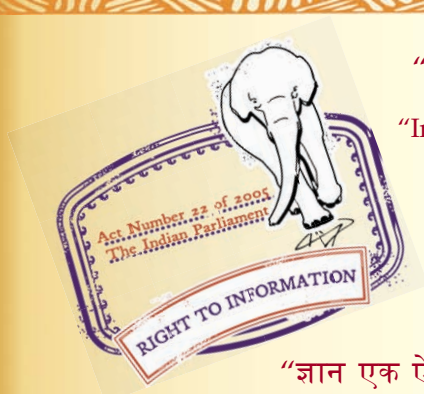

“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”

BLANK PAGE



Indian Standard

METHODS FOR CHEMICAL ANALYSIS OF STEELS

PART 2 DETERMINATION OF MANGANESE IN PLAIN-CARBON AND LOW ALLOY STEELS BY ARSENITE METHOD

(*Third Revision*)

(Second Reprint NOVEMBER 1998)

UDC 669.14+669.15-194.2 : 543 [546.711]

© *Copyright* 1987

BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

*Indian Standard*METHODS FOR
CHEMICAL ANALYSIS OF STEELSPART 2 DETERMINATION OF MANGANESE IN
PLAIN-CARBON AND LOW ALLOY STEELS
BY ARSENITE METHOD*(Third Revision)*Methods of Chemical Analysis of Ferrous Metals
Sectional Committee, SMDC 2*Chairman*

DR C. S. P. IYER

Representing

Bhabha Atomic Research Centre, Bombay

Members

SHRI G. M. APPARAO

Steel Authority of India Ltd (Bhilai Steel Plant),
BhilaiSHRI R. D. AGARWAL (*Alternate*)

SHRI S. V. BHAGWAT

Khandelwal Ferro Alloys Ltd, Nagpur

SHRI D. N. GUPTA (*Alternate*)

SHRI P. CHAKRA

Indian Metals & Ferro Alloys Ltd, Koraput

CHEMIST & METALLURGIST

Ministry of Transport (Department of Railways)

ASSISTANT RESEARCH OFFICER

(MET-2) RDSO, LUCKNOW

(*Alternate*)

CHIEF CHEMIST

Tata Iron & Steel Co Ltd, Jamshedpur

ASSISTANT CHIEF CHEMIST (*Alternate*)

SHRI M. K. CHAKRAVARTY

Ministry of Defence (DGI)

SHRI P. K. SEN (*Alternate*)

DR M. M. CHAKRABORTY

Indian Iron & Steel Co Ltd, Burnpur

SHRI M. S. CHATTERJEE (*Alternate*)

SHRI C. K. DIKSHIT

Ordnance Factory Board (Ministry of Defence),
CalcuttaSHRI S. N. MOITRA (*Alternate*)

SHRI V. B. KHANNA

Directorate General of Supplies & Disposals,
New Delhi

SHRI J. N. MUKHERJEE

Steel Authority of India Ltd (Durgapur Steel
Plant), Durgapur

(Continued on page 2)

© Copyright 1987

BUREAU OF INDIAN STANDARDS

This publication is protected under the *Indian Copyright Act* (XIV of 1957) and reproduction in whole or in part by any means except with written permission of the publisher shall be deemed to be an infringement of copyright under the said Act.

(Continued from page 1)

<i>Members</i>	<i>Representing</i>
SHRI P. NARAIN	Mahindra Ugine Steel Co Ltd, Bombay
SHRI G. R. SARMA (<i>Alternate</i>)	
SHRI N. P. PANDA	Steel Authority of India Ltd (Rourkela Steel Plant), Rourkela
SHRI B. MAHAPATRA (<i>Alternate</i>)	
DR L. P. PANDEY	National Metallurgical Laboratory (CSIR), Jamshedpur
DR D. C. PRASHAR	National Physical Laboratory (CSIR), New Delhi
SHRI J. RAI (<i>Alternate</i>)	
SHRI G. RAJARAO	Ferro Alloys Corporation Ltd, Shreeramnagar
SHRI K. RAMAKRISHNAN	Essen & Co, Bangalore
DR J. RAJARAM (<i>Alternate</i>)	
SHRI A. P. SINHA	Steel Authority of India Ltd (Bokaro Steel Plant), Bokaro
SHRI K. ANNIAH (<i>Alternate</i>)	
SHRI N. V. SUBBARAYAPPA	Visvesvaraya Iron & Steel Ltd, Bhadravati
DR P. SUBRAHMANYAM	Defence Metallurgical Research Laboratory, Hyderabad
SHRI T. H. RAO (<i>Alternate</i>)	
DR CH. VENKATESWARLU	Bhabha Atomic Research Centre, Bombay
SHRI K. RAGHAVENDRAN, Director (Struc & Met)	Director General, BIS (<i>Ex-officio Member</i>)
<i>Secretary</i>	
SHRI M. L. SHARMA Assistant Director (Metals), BIS	

Ferrous Metals Analysis Subcommittee, SMDC 2 : 3

<i>Convener</i>	
DR C. S. P. IYER	Bhabha Atomic Research Centre, Bombay
<i>Members</i>	
SHRI S. BASKARAN	Bharat Heavy Electricals Ltd, Hyderabad
SHRI MATA SARAN (<i>Alternate I</i>)	
SHRI B. RAHA (<i>Alternate II</i>)	
SHRI U. P. BOSE	Steel Authority of India Ltd (Bhilai Steel Plant), Bhilai
SHRI E. M. VERGHESE (<i>Alternate</i>)	
CHIEF CHEMIST	Tata Iron & Steel Co Ltd, Jamshedpur
ASSISTANT CHIEF CHEMIST (<i>Alternate</i>)	
DR M. M. CHAKRABORTY	Indian Iron & Steel Co Ltd, Burnpur
SHRI L. N. DAS (<i>Alternate</i>)	
SHRI H. K. DAS	Steel Authority of India Ltd (Rourkela Steel Plant), Rourkela
SHRI K. BISHNOI (<i>Alternate</i>)	
SHRI A. K. GUPTA	National Physical Laboratory (CSIR), New Delhi

(Continued on page 8)

Indian Standard

METHODS FOR CHEMICAL ANALYSIS OF STEELS

PART 2 DETERMINATION OF MANGANESE IN PLAIN-CARBON AND LOW ALLOY STEELS BY ARSENITE METHOD

(Third Revision)

0. FOREWORD

0.1 This Indian Standard (Part 2) (Third Revision) was adopted by the Indian Standards Institution on 16 January 1987, after the draft finalized by the Methods of Chemical Analysis of Ferrous Metals Sectional Committee had been approved by the Structural and Metals Division Council.

0.2 IS : 228, which was issued as a tentative standard in 1952, and revised in 1959, covered the chemical analysis of pig iron, cast iron and plain carbon and low alloy steels. For the convenience it was decided to publish a comprehensive series on chemical analysis of steels including high alloy steels. Accordingly, revision of IS : 228 was taken-up again and new series on methods of chemical analysis of steels including high alloy steels was published in various parts as IS : 228 (Parts 1 to 13) (*see* Appendix A) covering separate method of analysis for each constituent in steels. However, IS : 228-1959* version has been retained for the analysis of pig iron and cast iron till a separate standard for analysis of pig iron and cast iron is published.

0.2.1 This revision of IS : 228 (Part 2)-1972† has been undertaken on the basis of experience gained during the implementation of the standard by the manufacturers and testing laboratories.

0.3 In this revision major modifications are:

- a) modification of method for dissolution of low alloy steels, and

*Methods of chemical analysis of pig iron, cast iron and plain carbon and low-alloy steels (*revised*).

†Methods for chemical analysis of steels; Part 2 Determination of manganese in plain-carbon and low alloy steels by arsenite method (*second revision*).

- b) inclusion of reproducibility of the method at the various levels of manganese content.

0.4 Photometric method for determination of manganese up to 2 percent has been covered in IS : 228 (Part 12)-1976*.

0.5 In reporting the result of a test or analysis made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS : 2-1960†.

1. SCOPE

1.1 This standard (Part 2) covers method for the determination of manganese in plain carbon and low alloy steels by arsenite method.

2. SAMPLING

2.1 The samples shall be drawn and prepared as prescribed in the relevant Indian Standard.

3. QUALITY OF REAGENTS

3.1 Unless specified otherwise, analytical grade reagents and distilled water (see IS : 1070-1977)‡ shall be employed in the test.

4. DETERMINATION OF MANGANESE (0.1 TO 1.5 PERCENT) IN PLAIN CARBON AND LOW ALLOY STEELS BY THE ARSENITE METHOD (IN ABSENCE OF TUNGSTEN)

4.1 Outline of the Method — Manganese is oxidized, in presence of silver nitrate, to permanganic acid by ammonium persulphate and titrated with sodium arsenite solution.

4.2 Reagents

4.2.1 Dilute Nitric Acid — 1 : 2 (v/v).

4.2.2 Phosphoric Acid — 85 percent.

4.2.3 Dilute Sulphuric Acid — 1 : 4 (v/v).

*Methods for chemical analysis of steels: Part 12 Determination of manganese by periodate (photometric) method in low and high alloy steels (for manganese up to 2 percent) (second revision).

†Rules for rounding off numerical values (revised).

‡Specification for water for general laboratory use (second revision).

4.2.4 Concentrated Nitric Acid — Relative density 1.42 (conforming to IS : 264-1976*).

4.2.5 Ammonium Persulphate Solution — Freshly prepared, 10 percent (m/v).

4.2.6 Silver Nitrate Solution — 1 percent (m/v).

4.2.7 Sodium Chloride Solution — 1 percent (m/v).

4.2.8 Standard Sodium Arsenite Solution — Take 1.6 g of arsenious oxide in a 800-ml beaker. Add 10 g of sodium carbonate and 500 ml of water in the beaker and heat at low temperature until the solution is complete. Filter the solution through a filter pad in a bottle and make up the volume of the solution to 2 litres by addition of water. Shake the bottle vigorously. Standardize the arsenite solution as in 4.3 against 0.2 g of steel sample (having approximately similar composition as the sample under test) of known manganese content.

4.2.8.1 Adjust the strength of the sodium arsenite solution in such a way that each millilitre of the solution will be equivalent to 0.1 percent manganese when 0.2 g of sample is taken.

4.3 Procedure

4.3.1 Dissolution

4.3.1.1 Plain carbon steel — Take 0.2 g of an accurately weighed sample in a 250-ml conical flask. Add 10 ml of dilute nitric acid and 3 to 4 ml of phosphoric acid, and heat to dissolve the sample, boil to expel oxides of nitrogen and dilute to 100 ml.

4.3.1.2 Low alloy steel — Take 0.2 g of an accurately weighed sample in a 250-ml conical flask. Add 20 ml sulphuric acid and 2-3 ml of phosphoric acid. Heat until the reaction ceases. Add concentrated nitric acid drop by drop until the dissolution is complete, boil off nitrous fumes and dilute to 100 ml with water.

4.3.2 Add 20 ml of ammonium persulphate solution and boil. After few minutes of boiling, when the solution becomes clear, add 10 ml of silver nitrate and allow the colour of permanganic acid to develop. Boil to destroy the excess of persulphate. Cool quickly to room temperature.

*Specification for nitric acid (second revision).

4.3.3 Add 10 ml of sodium chloride solution to precipitate silver chloride. Titrate rapidly the permanganic acid with standard sodium arsenite solution until the pink colour is discharged.

5. CALCULATION

5.1 Calculate the manganese content of the steel as follows:

$$\text{Manganese, percent} = \frac{A \times B}{C} \times 100$$

where

A = volume of standard sodium arsenite solution used for titration,

B = manganese equivalent of standard sodium arsenite solution in g/ml, and

C = mass in g of sample.

5.2 Reproducibility

- a) ± 0.01 percent for manganese content below 0.06 percent,
- b) ± 0.02 percent for manganese content between 0.06 to 1 percent, and
- c) ± 0.03 percent for manganese above 1 percent.

APPENDIX A

(Clause 0.2)

IS : 228 Methods for chemical analysis of steels:

- (Part 1)-1972 Determination of carbon by volumetric method
(for carbon ≥ 0.1 percent) (*second revision*)
- (Part 2)-1972 Determination of manganese in plain carbon and low alloy steels by arsenite method (*second revision*)
- (Part 3)-1972 Determination of phosphorus by alkalimetric method
(*second revision*)
- (Part 4)-1974 Determination of carbon by gravimetric method
(for carbon ≥ 0.1 percent) (*second revision*)

- (Part 5)-1974 Determination of nickel by dimethylglyoxime (gravimetric) method (for nickel ≥ 0.5 percent) (*second revision*)
- (Part 6)-1974 Determination of chromium by persulphate oxidation method (for chromium ≥ 0.5 percent) (*second revision*)
- (Part 7)-1974 Determination of molybdenum by α -benzoinoxime method (for molybdenum > 1 percent) (*second revision*)
- (Part 8)-1975 Determination of silicon by the gravimetric method (for silicon ≥ 0.1 percent) (*second revision*)
- (Part 9)-1975 Determination of sulphur in plain carbon steels by evolution method (*second revision*)
- (Part 10)-1976 Determination of molybdenum by thiocyanate (photometric) method (for molybdenum up to 1 percent) in low and high alloy steels (*second revision*)
- (Part 11)-1976 Determination of silicon by photometric method in carbon steels and low alloy steels (for silicon 0.01 to 0.05 percent) (*second revision*)
- (Part 12)-1976 Determination of manganese by periodate (photometric) method in low and high alloy steels (for manganese up to 2 percent) (*second revision*)
- (Part 13)-1982 Determination of arsenic

(Continued from page 2)

Members

SHRI J. MUKHERJEE

SHRI P. K. BANERJEE (*Alternate*)

SHRI P. NARAIN

SHRI G. R. SARMA (*Alternate*)

SHRI R. S. NATH

SHRI N. GUNDAPPA (*Alternate*)

DR L. P. PANDEY

SHRI G. RAMDAS

SHRI R. D. VANDRIWALLA

SHRI J. C. DEY (*Alternate*)

Representing

Steel Authority of India Ltd (Durgapur Steel Plant), Durgapur

Mahindra Ugine Steel Co Ltd, Bombay

Steel Authority of India Ltd (Bokaro Steel Plant), Bokaro

National Metallurgical Laboratory (CSIR), Jamshedpur

Visvesvaraya Iron & Steel Ltd, Bhadravati

Italab Pvt Ltd, Bombay

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, NEW DELHI 110002

Telephones: 323 0131, 323 3375, 323 9402 Fax :+ 91 11 3234062, 3239399, 3239382

E - mail : bisind @ del 2.vsnl.net.in Internet : http://wwwdel.vsnl.net.in/bis.org

Central Laboratory:

Plot No. 20/9, Site IV, Sahibabad Industrial Area, Sahibabad 201010

Telephone

91-77 00 32

Regional Offices:

Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg, NEW DELHI 110002 323 76 17

*Eastern : 1/14 CIT Scheme VII, V.I.P. Road, Kankurgachi, CALCUTTA 700054 337 86 62

Northern : SCO 335-336, Sector 34-A, CHANDIGARH 160022 60 38 43

Southern : C.I.T. Campus, IV Cross Road, CHENNAI 600113 235 23 15

†Western : Manakalaya, E9, MIDC, Behind Marol Telephone Exchange, Andheri (East), MUMBAI 400093 832 92 95

Branch Offices:

'Pushpak', Nurmohamed Shaikh Marg, Khanpur, AHMEDABAD 380001 550 13 48

‡Peenya Industrial Area, 1st Stage, Bangalore-Tumkur Road, BANGALORE 560058 839 49 55

Commercial-cum-Office Complex, Opp. Dushera Maidan, Arera Colony, Bittan Market, BHOPAL 462016 72 34 52

62/63, Ganga Nagar, Unit VI, BHUBANESHWAR 751001 40 36 27

Kalai Kathir Building, 670 Avinashi Road, COIMBATORE 641037 21 01 41

Plot No. 43, Sector 16 A, Mathura Road, FARIDABAD 121001 91-28 88 01

Savitri Complex, 116 G.T. Road, GHAZIABAD 201001 91-71 19 98

53/5 Ward No.29, R.G. Barua Road, 5th By-lane, GUWAHATI 781003 56 65 08

5-8-56C, L.N. Gupta Marg, Nampally Station Road, HYDERABAD 500001 320 10 84

E-52, Chitaranjan Marg, C- Scheme, JAIPUR 302001 37 38 79

117/418 B, Sarvodaya Nagar, KANPUR 208005 21 68 76

Seth Bhawan, 2nd Floor, Behind Leela Cinema, Naval Kishore Road, LUCKNOW 226005 21 89 23

NIT Building, Second Floor, Gokulpat Market, NAGPUR 440010 52 51 71

Patliputra Industrial Estate, PATNA 800013 26 28 08

Institution of Engineers (India) Building 1332 Shivaji Nagar, PUNE 411005 32 36 35

'Sahajanand House' 3rd Floor, Bhaktinagar Circle, 80 Feet Road, RAJKOT 360002 26 85 86

T.C. No. 14/1421, University P. O. Palayam, THIRUVANANTHAPURAM 695034 32 72 15

*Sales Office is at 5 Chowringhee Approach, P.O. Princep Street, CALCUTTA 700072 27 10 85

†Sales Office is at Novelty Chambers, Grant Road, MUMBAI 400007 309 65 28

‡Sales Office is at 'F' Block, Unity Building, Narashimaraja Square, BANGALORE 560002 222 39 71